



ISSN: 0976-3376

Available Online at <http://www.journalajst.com>

ASIAN JOURNAL OF
SCIENCE AND TECHNOLOGY

Asian Journal of Science and Technology
Vol. 08, Issue, 01, pp.4084-4086, January, 2017

RESEARCH ARTICLE

STRENGTH PROPERTIES OF CONCRETE USING TERNARY SYSTEM

*Kannan, V.

Department of Civil Engineering, National College of Engineering, Maruthakulam,
Tirunelveli, Tamilnadu, India

ARTICLE INFO

Article History:

Received 20th October, 2016
Received in revised form
15th November, 2016
Accepted 22nd December, 2016
Published online 31st January, 2017

Key words:

Concrete; Silica fume;
Ground Granulated
Blast Furnace Slag;
Ternary system;
Mechanical Properties.

ABSTRACT

Utilization of industrial waste materials and other supplementary materials in concrete compensates the lack of natural resources, solving the disposal problem of waste and to find alternative technique to safeguard the nature. Also it can be used to enhance the mechanical and durability properties of the concrete. There are a number of supplementary materials such as silica fume (SF), Ground Granulated Blast Furnace Slag (GGBFS), Fly Ash (FA), Rice Husk Ash (RHA) and more used as partial replacement of cement. This paper carries out a thorough assessment about the addition of SF and GGBFS, which can be adequately utilized in concrete as cement substitution. For that water cement ratio was fixed as 0.55 and the replacement level is from 5% to 20%. Totally nine mix were prepared in the range of 0 to 25 % of SF and GGBFS in binary and ternary system. Different properties were studied to identify optimum level of replacement such as physical properties, chemical properties of materials and mechanical properties.

Copyright©2017, Kannan. This is an open access article distributed under the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

INTRODUCTION

Concrete is the most widely used construction material in the world. The utility and elegance as well as the durability of concrete structures, built during the first half of the last century with Ordinary Portland Cement (OPC). The Ordinary Portland Cement (OPC) is one of the main ingredients used for the production of concrete and has no alternative in the civil construction industry. The only defect in the use of concrete is that it is weak in tension. Since the concrete is weak in tension the possibility of formation of crack is more. Silica fume is a by-product of producing silicon metal or ferrosilicon alloys. Silica fume consists primarily of amorphous (non-crystalline) silicon dioxide (SiO₂). The individual particles are extremely small, approximately 1/100th the size of an average cement particle. When silica fume is added to concrete, initially it remains inert. The addition of silica fume to concrete improves the latter's durability by reducing permeability and refining pore structure, leading to a reduction in the diffusion of harmful ions and the calcium hydroxide content, resulting in greater resistance to sulfate attack. GGBFS is a recyclable material created when the molten slag from melted iron ore is quenched rapidly and then ground into a powder. This material has cementitious properties and has been used as a replacement for cement for over 100 years.

If the molten slag is cooled and solidified by rapid water quenching to a glassy state, little or no crystallization occurs. This process results in the formation of sand size (or frit-like) fragments, usually with some friable clinker like material. The physical structure and gradation of granulated slag depend on the chemical composition of the slag, its temperature at the time of water quenching, and the method of production. When crushed or milled to very fine cement-sized particles, ground granulated blast furnace slag (GGBFS) has cementitious properties, which make a suitable partial replacement for or additive to Portland cement.

Research Significance

SF and GGBFS are the effective cement replacement materials. Both materials are accepted and using (in binary system) for the strength and durability properties improvement in concrete, but the studies on ternary system of SF with GGBFS is limited. Hence this paper, mainly focusing the use of ternary system of SF with GGBFS in the strength improvement of concrete. When used in certain proportions, SF and GGBFS (binary and ternary system) have shown to increase the compressive strength and splitting tensile strength of concrete. The experimental research conducted in this study showed the mechanical properties of concrete have improved when SF and GGBFS were used as partial replacement of sand in specified percentages (5% to 25%).

*Corresponding author: Kannan, V.,

Department of Civil Engineering, National College of Engineering,
Maruthakulam, Tirunelveli, Tamilnadu, India.

MATERIALS AND MATERIALS

Cement: Ordinary Portland Cement (OPC) of 53 grade was used.

Fine Aggregate: River sand of specific gravity of 2.41 with 4.5 mm size was used.

Coarse Aggregate: Well graded coarse aggregate of specific gravity of 2.6 with 22 mm size was used.

Water: Potable water is used for all mixes.

SF and GGBFS: Commercially available SF and GGBFS were used for entire experimental work.

EXPERIMENTAL WORKS

Preparation of SF and GGBFS test specimen

Commercially available SF and GGBFS were collected and were dried before use. The cement and SF and GGBFS were mixed thoroughly in binary (OPC + SF / GGBFS) and ternary (OPC + SF + GGBFS) system. Further sand and coarse aggregate were added to the mix. The materials were mixed in dry conditions for few minutes. Once all the materials were mixed well, the water was added to the dry mix in a standard concrete mixer. The resulting concrete mix was used to prepare $150 \times 150 \times 150$ mm (6 in \times 6 in \times 6 in) cubes and 150 mm \times 300 mm (6 in \times 12 in) cylinders. The concrete was poured into the molds and was compacted 25 blows by a compaction rod. After that the cubes, beams, and cylinders were vibrated for 1 to 2 min on a vibrating machine and then the top surface of the specimens was finished using a trowel. After that, the molds were left to dry for 24 hours. The specimens were then removed from the molds and were cured in water tank for curing for 28 days. The curing time was not a parameter in this study and hence no comparisons were made for the effect of SF and GGBFS on curing time. Several mixes were prepared with different percentages of granite powder as partial replacement of sand. All other ingredients were kept the same. The percentages of SF / GGBFS used were 0%, 5%, 10%, 15%, and 20% as binary system and SF + GGBFS used were 0%, 5% + 5%, 5% + 10%, 5% + 15%, 5% + 20% of cement. The mixes proportions for the mixes tested in this study are shown in Table 1. A total of nine mixes were tested: M0 – M8 by weight of cement respectively.

Table 1. Mix Details

Mix ID	Mix Descriptions
M0	100% OPC
M1	95% OPC + 5% GGBF
M2	90% OPC + 10% GGBF
M3	85% OPC + 15% GGBF
M4	80% OPC + 20% GGBF
M5	90% OPC + 5%SF +5% GGBF
M6	85% OPC + 5%SF+10% GGBF
M7	80% OPC + 5%SF +15% GGBF
M8	75% OPC + 5%SF+20%GGBF

Experimental works

To check the fresh state properties such as slump cone test and compaction factor test were conducted according to Indian code specifications. The compressive strength test was carried

out after 28 days, and split tensile tests were conducted over 28 days of water curing. The compressive strength and splitting tensile strength tests were carried out according to IS 516-1956 and IS 5816: 1999 respectively.

RESULTS AND DISCUSSION

Compressive strength

The test results for compressive strength of concrete on 28 days with 5%,10%,15% and 20% replacements of cement with the combination of GGBFS and Silica fume are tabulated as follows (Figure 1).

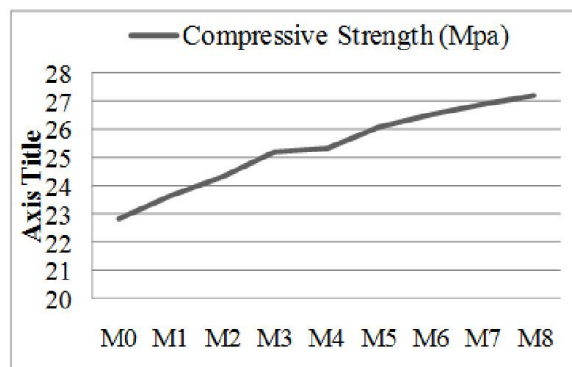


Figure 1. Compressive strength of concrete

At 7days, by comparing the compressive strengths of normal concrete, 5%GGBS, 10%GGBS, 15%GGBS, and 20% GGBS the last combination i.e, 20%GGBS achieves maximum strength of 25.3 N/mm^2 . At 7days, by comparing the compressive strengths of normal concrete, 5%GGBS & 5% SF, 10%GGBS &5% SF and 15%GGBS & 5% SF, the last combination i.e,20%GGBS & 5% SF achieves maximum strength of 27.2 N/mm^2 .

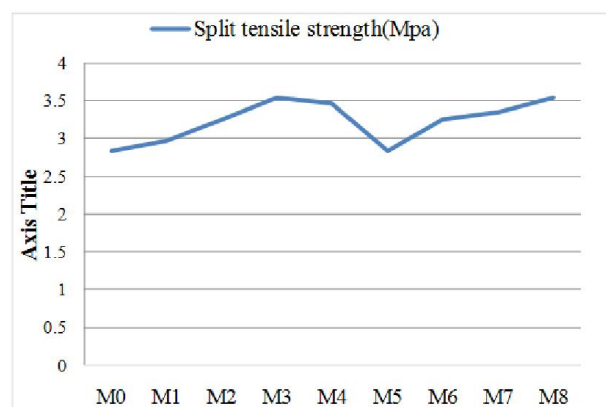


Figure 2. Split Tensile strength of concrete

Split tensile strength

The test results for tensile strength of concrete on 28 days with 5%, 10%, 15% and 20% replacements of cement with the combination of GGBFS and Silica fume are tabulated as follows (Figure 2). At 7days, by comparing the split tensile strengths of normal concrete, 5%GGBS, 10% GGBS, 15% GGBS, and 20%GGBS the last combination i.e, 15%GGBS achieves maximum strength of 3.54 N/mm^2 . At 7days, by comparing the split tensile strengths of normal concrete, 5%GGBS & 5% SF, 10%GGBS &5% SF,15%GGBS & 5%

SF and 20%GGBS & 5% SF the last combination i.e.,20%GGBS & 5% SF achieves.

Conclusion

Based on limited study carried out on performance of GGBFS and Silica fumes concrete in comparison with normal concrete of design strength of M20 following conclusion are drawn

- Use of GGBFS as cement replacement increases consistency.
- As the replacement level of cement by GGBFS increases there is an increase in split tensile strength & compressive strength for M20 grade of concrete up to 20% replacement level, and beyond that level there is a decrease in split tensile.
- As the replacement of cement with different percentages with Silica fume increases the consistency increases.
- As the replacement level of cement by silica fume increases there is an increase in split tensile strength for M20 grade of concrete up to 5% replacement level, and beyond that level there is a decrease in split tensile and Compressive strength.
- The consistency and setting time (the initial and the final) of the cement increased with the increase of GGBFS contents. Water demands of blended cements are higher than that of pure cement paste. The increase in initial setting time of GGBFS incorporated cement paste is higher than the increase of final setting time with respect to cement paste. It indicates that the addition of GGBFS retards the initial hydration of cements.
- The compressive strength of concrete is decreasing at all ages with the increasing replacement of GGBS in cement concrete. However, the effect of replacement of GGBFS in compressive strength test is not so distinct in M3 and M4 specimen at 28 days.
- The compressive strength of silica added concrete mixes has shown good improvement in early age's compressive strength as compared with the GGBFS cement mix. The early age compressive strength of silica added M6 and M7 is comparable, even better than control concrete.

REFERENCES

Bayasi, Zing, Zhou, Jing, 1993. "Properties of Silica Fume Concrete and Brooks JJ, Al-Kaisi AF. Early strength development of portland and slag cement concretes cured at elevated temperatures, *ACI Materials Journal*, 87(1990) 503-7.

Bhanja, S., Sengupta, B. 2003. "Modified water-cement ratio law for silica fume concretes", *Cement and Concrete Research*, Vol. 33, 447-450.

Bhikshma, V., Nitturkar, K. and Venkatesham, Y. 2009. "Investigations on mechanical properties of high strength silica fume concrete." *Asian journal of civil engineering (building and housing)* vol. 10, no. 3, pp.335-346.

Douglas, E, Pouskouleli, G. 1991. Prediction of compressive strength of mortars made with Portland cement - blast furnace slag - fly ash blends, *Cement and Concrete Research*, 21. 523-34.

Ganesh Babu, K. and Sree Rama Kumar, V. 2000. "Efficiency of GGBS in Concrete", *Cement and Concrete Research*, Vol. 30,, 1031-1036.

Haque, M.N., Chulilung, T. 1990. Strength development of slag and ternary blend concrete, *Cement and Concrete Research*, 20, 120-30.

IS 10262: 1982. "Recommended Guidelines for Concrete Mix design", Bureau of Indian Standard, New Delhi

IS 383: 1970. "Specification for Coarse aggregate and Fine aggregate from Natural Sources for Concrete", Bureau of Indian Standard, New Delhi

IS 456: 2000. "Indian Standard Code of Practice for Plain and Reinforced Concrete", Bureau of Indian Standard, New Delhi

Jiayong, L. and Pei, T. 1997. Effect of slag and silica fume on mechanical properties of high strength concrete, *Cement and Concrete Research*, 27, 833-7.

Joshi, N. G. 2001. Bandra - Worli Sea Link: Evolution of HPC mixes containing Silica Fume, *Indian Concrete Journal*, (Oct.), pp. 627-633

Kanstad, T, Biontegaard, O, Sellevold, E. J, Hammer, T. A. and Fidjestol, P. Effect of Silica Fume on Crack Sensivity, *Concrete International*, (Dec. 2001), pp 53-59

Lewis, R. C., Hasbi, S. A. 2001. Use of Silica Fume concrete : Selective case studies, *Indian Concrete Journal*, (Oct.), pp. 645-652.

Miura, T., Iwaki, I. 2000. Strength development of concrete incorporating high levels of ground granulated blast-furnace slag at low temperatures, *ACI Materials Journal*, 97. 66-70.

Mortar", *ACI Materials Journal* 90 (4) 349 - 356.

Olorunsogo, F.T. and Wainwright, P.J. 1998. Effect of GGBFS particle-size distribution on mortar compressive strength, *ASCE Journal of Materials in Civil Engineering*, 10, 180-7.

Oner, A. and Akyuz, S. 2007. "An experimental study on optimum usage of GGBS for the compressive strength of concrete", *Cement & Concrete Composite*, Vol. 29, , 505-514.

Pierre-Claude Aitcin, 2003. "The durability characteristics of high performance concrete", *Cement & Concrete Composite*, Vol. 25, 409-420.

Ray, I, De, A and Chakraborty, Fifth Conference on Concrete Technology for High Slump Concrete, Vol 1, p.p 86-93

Roncero, J., Gettu, R., Agullo, L., Vazquez, E. 2002. Flow behaviour of superplasticised cement pastes : Influence of Silica Fume, *Indian Concrete Journal*, (Jan), pp. 31-35.

Saini, S, Dhuri, S. S, Kanhere, D. K, Momin, S. S. 2001. High Performances concrete for an urban viaduct in Mumbai, *Indian Concrete Journal*, pp. 656-664.

Swamy, R.N., Bouikni, A. 1990. Some engineering properties of slag concrete as influenced by mix proportioning and curing, *ACI Materials Journal*, 87. 210-220.

Tan, K., Pu, X. 1998. Strengthening effects of finely ground fly ash, granulated blast furnace slag, and their combination, *Cement and Concrete Research*, 28, 1819-25.

Venkatesh Babu, D.L., Nateshan, S.C. 2003. Investigations on silica fume concrete, *The Indian concrete Journal*, September, pp. 57-60.

Vishnoi, R. K., Gopalakrishnan, M. 2003. Tehri Dam Project : Silica Fume in High Performance Concrete for Ensuring Abrasion Erosion Resistance, Proceedings organised by Indian Society for Construction Materials and Structures, (February), pp. 28-40.